



Properties of Particleboard Manufactured from Commonly Used Bamboo (*Bambusa vulgaris*) Wastes in Bangladesh

D. M. Nazmul Alam¹, Khandkar- Siddikur Rahman^{1*}, Sourav Bagchi Ratul¹, Arifa Sharmin¹, Tania Islam², Md. Abu Wabaeid Hasan¹ and Md. Nazrul Islam¹

¹Forestry and Wood Technology Discipline, Khulna University, Khulna-9208, Bangladesh.

²Department of Public Administration, Government of the People's Republic of Bangladesh, Dhaka, Bangladesh.

Authors' contributions

This work was carried out in collaboration between all authors. Authors DMNA and MNI designed the study. Authors DMNA, MAWH and SBR performed the experimental study, and authors DMNA and SBR wrote the first draft of the manuscript. Authors AS, TI and MAWH managed the literature searches, and authors KSR and AS managed the analysis of data and Authors KSR, TI and MNI wrote the final manuscript. All authors read and approved the final manuscript.

Article Information

DOI:10.9734/AIR/2015/15581

Editor(s):

(1) Graham Ormondroyd, The Bio Composites Centre, Bangor University, UK.

Reviewers:

(1) Anonymous, Turkey.

(2) Anonymous, Greece.

(3) Silvana Nisgoski, Department of Forest Engineering and Technology, Federal University of Parana, Brazil.

Complete Peer review History: <http://www.sciencedomain.org/review-history.php?iid=969&id=31&aid=8347>

Original Research Article

Received 5th December 2014

Accepted 10th February 2015

Published 4th March 2015

ABSTRACT

Aims: This paper explores the properties of single layer particleboard produced from bamboo wastes and branches.

Experimental: Three types of single layer particleboard i.e., branch-waste mixed particleboard (WB_{PB}), bamboo branch particleboard (B_{PB}) and bamboo wastes (shavings obtained during planning operation of bamboo) particleboard (W_{PB}) were manufactured with 15% urea formaldehyde (UF) resin. Physical and mechanical properties of the manufactured particleboards were evaluated according to the ASTM D-1037 standard.

Results: Results showed that the physical properties i.e., density, moisture content (MC), water absorption (WA), thickness swelling (TS), linear expansion (LE) and mechanical properties i.e.

*Corresponding author: E-mail: rana_ksr@yahoo.com

modulus of elasticity (MOE) and modulus of rupture (MOR) of bamboo branch-waste mixed particleboard (WB_{PB}) was better than bamboo branch particle board (B_{PB}) and bamboo wastes particle board (W_{PB}). It was found that the density of B_{PB} , W_{PB} and WB_{PB} were 742, 846 and 1024 kg/m^3 , respectively. Thickness swellings of B_{PB} , W_{PB} and WB_{PB} after 24 hours of immersion were 32.33, 19.6 and 16.3%, respectively. Water absorption rate of B_{PB} , W_{PB} and WB_{PB} particleboards were 81, 64.3 and 39.8%, respectively. Modulus of rupture of B_{PB} , W_{PB} and WB_{PB} were 16.8, 18 and 21.6 N/mm^2 , respectively.

Conclusion: All these three types of particleboard followed the American National Standard ANSI A208.1 requirements for physical and mechanical properties of particleboard.

Keywords: Bamboo particles; urea formaldehyde (UF) resin; physical properties; bending strength.

1. INTRODUCTION

In the last 40 years successful development of wood based panels with the economic advantage of low cost wood and other lignocellulosic materials is the proficient alternative of solid wood. The demand of composite wood products such as particleboard, plywood, hardboard, oriented standard board, medium density fiberboard and veneer board has hiked significantly throughout the world [1]. Among them, the demand of particleboard has been increasing significantly because of house construction, interior decoration, manufacturing of furniture [1,2] flooring, home constructions, countertops, stair treads, cabinets, tabletops, vanities, speakers, sliding doors, lock blocks, interior signs, displays, table tennis, pool tables, electronic game consoles, kitchen work tops, and work surfaces in offices, educational establishments, laboratories and other industrial products [3]. This huge demand of particleboard accelerates the declining rate of natural forest resources. Consequently, it has raised a vital issue of the continuous supply of raw material to the wood based sectors [4]. Thus, the demand of alternative sources of raw materials is increasing ever more. Alternate lignocellulosic materials like agricultural residues and non-woody plant fibers may play a major role in minimizing the demand of manufacturing the composite panels [3].

Bamboo is a giant woody grass and belongs to group angiosperms and order monocotyledon [5]. There are about 1,200-1,500 bamboo species under 60 to 70 genera, all over the world [6]. Bamboo is a renewable raw material universally accepted for building construction. It has a fundamental role in industrial and domestic economics in many developing countries. Bamboo culm consists most of the woody portion which is straight, cylindrical and hollow-formed of nodes and internodes. Compared with some commercial wood species, bamboo exhibits

equal or better physical and mechanical properties, which offer good potential for processing it into composites (bamboo-based panels) as a wood substitute [7]. The bamboo-based industries have developed into a multi-million dollar industry with their variety of products enjoying very high demand domestically as well as internationally. Similarly to other countries, value-added laminated bamboo panels were developed in Bangladesh from two common locally found species named *Bambusa balacooa* and *Bambusa vulgaris*. The panels made from bamboo have been found suitable for different end-uses [8]. But only 3.6 m from base of *B. vulgaris* found usable in an economic point of view as laminated bamboo panels. During the production of these products, more than 30% of the bamboo like branches, nodes, rhizomes and lower portion of the culm, etc. are left unused and treated as wastage [8]. These bamboo wastes are mostly used as fuel. These unused portions can be used as raw material for particleboard industries. Although many studies have been conducted on bamboo particleboards for development of local bamboo based industries, but none of them explores the utilization of bamboo wastage for particleboard production. Therefore, the aim of this study is to produce single layer particleboard with UF resin from the bamboo wastes and branches and evaluation of their properties.

2. EXPERIMENTAL

2.1 Materials Preparation

Wastage of mature village grove bamboo (*Bambusa vulgaris*) of 3 years old was used in this experiment and branches were collected. Wastage and branches were chipped with an improvised chipper. These chips were further grinded in a laboratory grinder to convert them into particles. After grinding, each type of raw

materials was screened in 1 and 2 mm opening mesh to eliminate the undersized and oversized particles. Particles were dried in an oven (SANFA, model: 9101-ISA. Sr no: 5054) for 24 hours with $103\pm 2^{\circ}\text{C}$ temperature to reduce the moisture content up to 4%. Liquid urea formaldehyde glue (48% solid content) was used as a binder. The proportion of urea formaldehyde resin was 15% of dry weight basis of particles. The flower was used as an extender and NH_4Cl was used as a hardener. The wax was added to improve the moisture resistance at a rate of 1% on the dry weight basis of particles.

2.2 Panel Manufacturing

The dried particles were manually blended with UF resin. Three different types of particleboards were manufactured i.e., bamboo branch particleboard (B_{PB}), bamboo waste particleboard (W_{PB}) and bamboo branch waste mixed particleboard (WB_{PB}) by following the same process. The ratio of branch and node in bamboo branch waste mixed particleboard (WB_{PB}) was 1:1. The target size of the particleboard was 30×20 cm with the thickness of 12 mm. After blending the mat of the particles was formed manually. The mats were then pressed in a hot press (DZ47-63, D32) for 8 minutes at the temperature of 130°C and specific pressure of 4.5 N/mm^2 . After hot pressing, the mats were further cool pressed for 15 minutes for avoiding spring back of particleboards. The boards conditioned in a conditioning room for 48 hours prior to stacking to avoid degradation of the urea formaldehyde resins. Finally, the boards were trimmed to reduce the edge effect during testing.

2.3 Laboratory Test

All tests were carried out in accordance with ASTM D-1037 [9] standard after conditioning all the specimens for 48 hours at room temperature. At least six specimens were collected from each type of panel for testing the physical and mechanical properties. Modulus of rupture (MOR), modulus of elasticity (MOE), density, water absorption (WA), linear expansion (LE) and thickness swelling (TS) were measured. The MOR and MOE were measured by using Universal Testing Machine (IMAL-IB600). WA and TS samples were fully immersed in distilled water at 25°C for 24 hours.

2.4 Statistical Analysis

Average and standard deviation was calculated for different properties. SAS statistical software (version 6.2) was used for the data analysis. ANOVA and LSD (least significant difference) test were carried out to evaluate the significance of differences among the properties of panels.

3. RESULTS AND DISCUSSION

Statistical analysis of physical and mechanical properties of the boards is shown in Tables 1 and 2. Analysis of variance (ANOVA) was used to assess any co-relation between boards of different particle types (bamboo wastages and branches).

3.1 Density

The density of particleboards made from bamboo branches (B_{PB}), bamboo wastes (W_{PB}) and bamboo branch-waste mixed (WB_{PB}) were shown in Fig. 1. The results showed that WB_{PB} particle board has higher density than those of the particleboard made from bamboo wastes (W_{PB}) and bamboo branches (B_{PB}) using the same resin as an adhesive. This effect can be due to the raw materials density which affects the particleboard density. The density of bamboo 648 kg/m^3 (40.5 lb/ft^3) and higher specific gravity of bamboo ranged from 0.3 to 0.8 [10]. The bamboo culm waste contains shavings of peripheral layer of bamboo and holds greater density because of higher frequency of vascular bundle present in peripheral layer [11,12]. Higher frequency of vascular bundle influence higher density in most of the bamboos [13]. But bamboo branch cell wall contains higher lignin content compared to culm cell wall [14]. This high lignin content may make up the lignin lacking and resulting greater density of mixed particleboard (WB_{PB}). Significant difference (when $F = 78.37$, $df = 2, 24, 26$ and $P < 0.05$) of density within B_{PB} , W_{PB} and WB_{PB} was found in ANOVA analysis (Table. 1). Compared with other related works the value of these particleboards were substantially higher than that of saline Athel wood particleboard 720 kg/m^3 [15]. But WB_{PB} particle board shows higher density and remains two show lower densities compared to bamboo waste particleboards [16]. According to American National Standard [17] only bamboo branch particleboard (B_{PB}) was in the range of medium density particleboard ($610\text{-}800 \text{ kg/m}^3$) and another two types of particleboard i.e., bamboo

wastes particleboard (W_{PB}) and bamboo branch-waste mixed particleboard (WB_{PB}) were high density particleboard (above 800 kg/m^3).

3.2 Modulus of Elasticity (MOE)

Modulus of Elasticity of B_{PB} , W_{PB} and WB_{PB} particleboards were showed in Fig. 2. Modulus of Elasticity affected similarly by density. Increasing board density increases modulus of elasticity; increasing surface density and surface particle alignment also increases modulus of elasticity. From the ANOVA, it has been observed that, there was significant difference present (when $F = 29.21$, $df = 2, 12, 14$ and $P < 0.05$), between the B_{PB} , W_{PB} and WB_{PB} particleboards (Table. 1). It was also observed that the mean Modulus of Elasticity of B_{PB} and W_{PB} particleboard was lower compared with the MOE of Malaysian bamboo *Gigantochloa scortechinii* particleboard (2696 N/mm^2) [18] and it was found that only the MOE of WB_{PB} was higher. The MOE of these three boards was also compared with the MOE of Athel wood particleboard [10] and bamboo waste particleboards [16]. It was found that the MOE of B_{PB} was lower but MOE of W_{PB} and WB_{PB} was

higher (Fig. 2). According to American National Standard [17] MOE of particleboard range from $1725\text{-}2750 \text{ N/mm}^2$ and all the three types of particleboard follow the range of the standard.

3.3 Modulus of Rupture (MOR)

The MOR of B_{PB} , W_{PB} and WB_{PB} particleboard were presented in Fig. 3. It is observed that the mean Modulus of Rupture of B_{PB} and W_{PB} particle boards were lower except WB_{PB} particleboard compared with particleboard made from *Bambusa vulgaris* bamboo waste particleboards [16]. It was found that only B_{PB} is lower, W_{PB} is nearly equal and WB_{PB} is greater than *Bambusa vulgaris* bamboo waste particleboard. From the ANOVA, it has been observed that, there were significant difference (when $F = 29.28$, $df = 2, 12, 14$ and $P < 0.05$) present for MOR between B_{PB} , W_{PB} and WB_{PB} particleboard (Table. 1). According to American National Standard [17] MOR of particleboards ranges from $16.5\text{-}23.5 \text{ N/mm}^2$ and all the three types of particleboard are in this range of the standard.

Table 1. Statistical analysis of density, MOR and MOE of three particleboards

Types of particleboard	Thickness (mm)	Properties		
		Density(kg/m^3)	MOR(N/mm^2)	MOE(N/mm^2)
B_{PB}	12	742 ^C (4.62)	16.8 ^C (0.51)	1995 ^C (100.73)
W_{PB}	12	846 ^B (3.58)	18 ^B (0.41)	2243 ^B (173.6)
WB_{PB}	12	1024 ^A (6.06)	21.6 ^A (1.48)	2752 ^A (290.47)

Values in parenthesis are standard deviation
Values within the same line column by different letters are significantly different

Table 2. Statistical analysis of dimensional stability of three particleboards

Types of particleboard	Thickness (mm) mean	Properties		
		WA(%)	LE(%)	TS(%)
B_{PB}	12	81 ^A (5.06)	0.98 ^A (0.01)	32.33 ^A (0.7)
W_{PB}	12	64.3 ^B (2.2)	0.86 ^B (0.065)	19.6 ^B (2.39)
WB_{PB}	12	39.8 ^C (10.77)	0.67 ^C (0.03)	16.3 ^C (1.13)

Values in parenthesis are standard deviation
Values within the same line column by different letters are significantly different

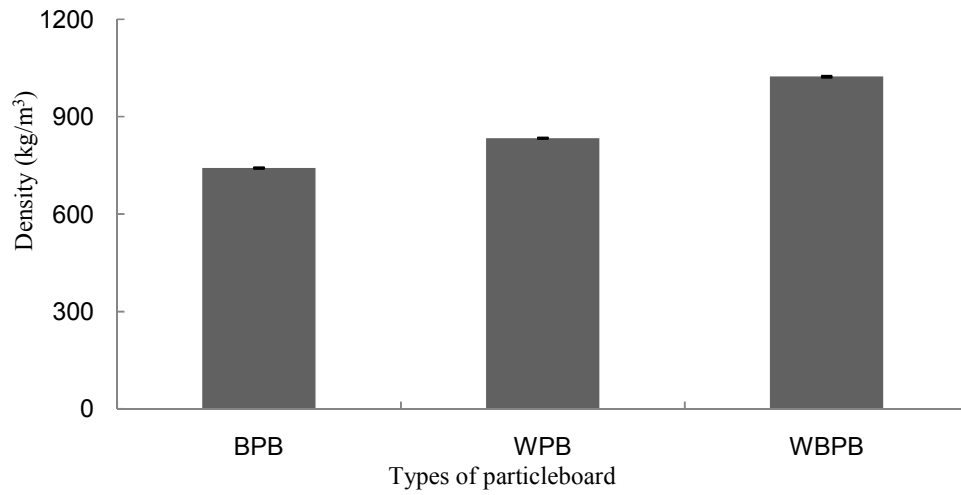


Fig. 1. Density of three types of particleboard

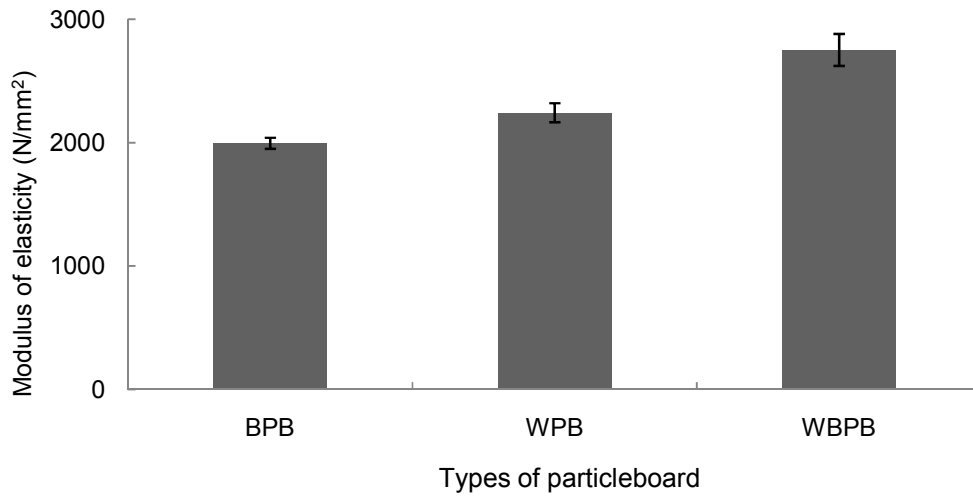


Fig. 2. Modulus of elasticity (MOE) of three types of particleboard

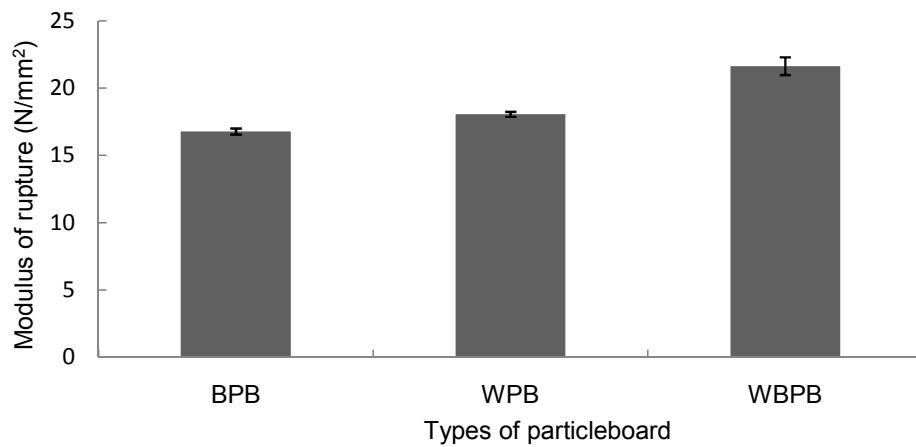


Fig. 3. Modulus of rupture (MOR) of three types of particleboard

3.4 Dimensional Stability

In general, the water absorption, thickness swelling, and linear expansion value of particleboard made from bamboo branch, bamboo waste and the mixed particle board increased with increasing in soaking time. It was found that after 24 hours the percentage of water absorption capacity of B_{PB} particleboard, W_{PB} particleboard and WB_{PB} particleboard were 81%, 64.3% and 39.8% respectively. Swelling percentage in length of B_{PB}, W_{PB} and WB_{PB} particleboard were 0.98%, 0.86% and 0.67% respectively, and the percentage of thickness swelling of B_{PB} particleboard, W_{PB} particleboard and WB_{PB} particleboard were 32.33%, 19.6% and 16.3% respectively (Figs. 5 and 6). According to American National Standard [17] the mean linear expansion and thickness swelling values for all three types of board will exceed the critical value of 0.35 percent and 1.6 percent.

The water absorption in the 24-hour water soak test was highly correlated with the board density [19], particle hygroscopicity, spring back and water absorption affinity of the binding materials [16]. For all formulations, the higher compaction ratio always absorbed a lower amount of water than the lower compaction ratio. Water entry into the higher density boards occurred at a slower rate due to the decreased porosity and the increased wood material [20]. If density increases porosity will decrease. So here high density board WB_{PB} has absorbed less water than the other two types of board (Fig. 4). Used urea formaldehyde adhesive has water affinity

characteristics and absorbs moisture when it's exposed to moist conditions [16].

Tomalang et al. [21] described that higher holocellulose content of bamboo mainly responsible for the water absorption of particleboard. The density and water absorption capacity have more effect on thickness swelling and linear expansion of particleboard. Higher density board absorbs less water than a lower density board, so the thickness swelling and the linear expansion percentage of higher density WB_{PB} is lower than other two particleboards (Figs. 5 and 6). Especially B_{PB} absorbs more water and it may happen in chemical composition varies between bamboo and bamboo branch. Analysis of variance shows significant difference was present between B_{PB}, W_{PB} and WB_{PB} particleboard in water absorption, thickness swelling and linear expansion ($F = 43.79$, $df = 2, 12, 14$ and $p < 0.05$ for WA, $F = 1.064$, $df = 2, 12, 14$ and $p < 0.05$ for LE and $F = 14.85$, $df = 2, 12, 14$ and $p < 0.05$ for TS) (Table. 2). WA and TS of three types of particleboard were compared with *Bambusa vulgaris* bamboo waste particleboards [16] where all show higher water absorption and thickness swelling. It is also observed that the mean linear expansion of B_{PB}, W_{PB} and WB_{PB} were 0.98%, 0.86% and 0.67%. Compared to bagasse particleboard [22] 0.92%, it was found that only WB_{PB} is higher but B_{PB} and W_{PB} are lower than the bagasse particleboard. The findings of the properties of this study are comparable to the commercial particleboard produced in Bangladesh and much higher than the results of experimental particleboards as reported by Ashaduzzaman and Sharmin [23].

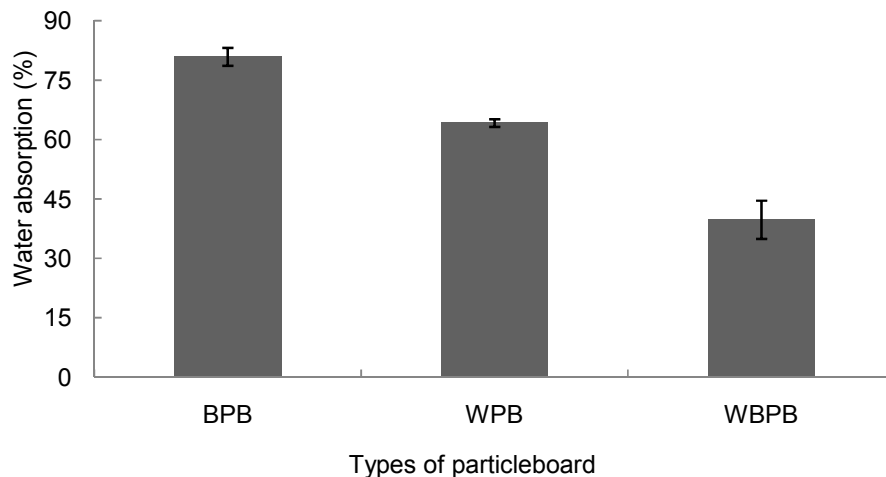


Fig. 4. Water absorption of three types of particleboard

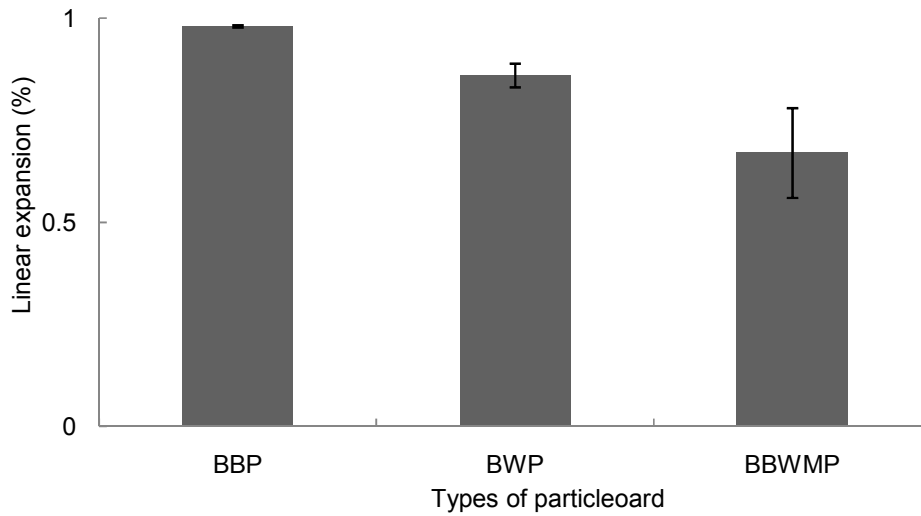


Fig. 5. Linear expansion of three types of particleboard

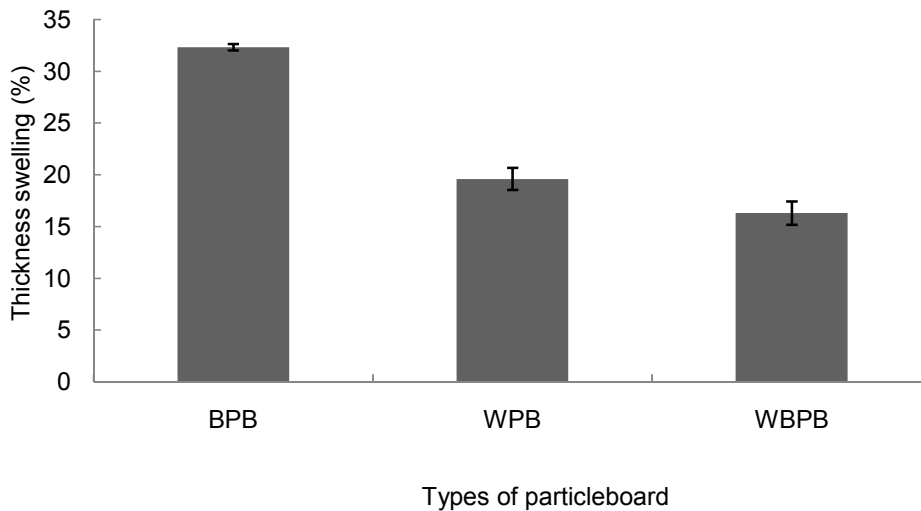


Fig. 6. Thickness swelling of three types of particleboard

4. CONCLUSION

The study investigated the properties of single layer particleboards manufactured from branch and the waste of *Bambusa vulgaris* with UF resin. The above results suggest that the produced particleboard from the branches and wastages is technically feasible, which ensures the optimum utilization of renewable biomass. From the results and discussion, the following specific conclusion can be drawn:

1. Bamboo culm waste showed greater density, MOE and MOR than bamboo

branch particleboard. But a mixture of culm waste and branch at same content showed much greater density, MOE and MOR between three type particleboards.

2. Particleboard with higher strength and dimensionally stable can be produced from the bamboo wastes particleboard.

COMPETING INTERESTS

Authors have declared that no competing interests exist.

REFERENCES

1. Sellers T. Growing markets for engineered products surplus research. Wood Technology. 2000;127(3):40-4.
2. Pan, Z. Catcart, A. Properties of particleboard bond with rice bran and polymeric methylene diphenyl diisocyanate adhesives. Ind. Crops Prod. 2006;23(1):40-45.
3. Nemli G, Aydin A. Evaluation of the physical and mechanical properties of particleboard made from the needle litter of *Pinus pinaster* Ait. Ind Crops Prod. 2007; 26(3):252–8.
4. Çolak S. Çolakoglu G. Aydin I. Kalaycioglu H. Effects of steaming process on some properties of eucalyptus particleboard bonded with UF and MUF adhesives. Build Environ. 2007;42(1):304–9.
5. Chapman GP. The biology of grasses. Department of Biochemistry and Biological Sciences, Wye College, University of London, U.K. CAB International. 1996;14-19.
6. Wang D, Shen SJ. Bamboos of China. Timber Press, Portland, Oregon; 1987.
7. Sumardi I, Ono K, Suzuki S. Effect of board density and layer structure on the mechanical properties of bamboo oriented strand board. J. Wood Sci. 2007;53:510-515.
8. Biswas D. Bamboo as an alternative to wood for composites manufacture. PhD dissertation. Institute of Forestry and Environmental Sciences, Chittagong University, Chittagong Bangladesh; 2008.
9. ASTM (American Society for Testing Materials). Standard test methods for evaluating properties of wood-based fiber and particle panel materials static tests of timbers, D 1037- 93, ASTM, Philadelphia, PA; 1999.
10. Lee AWC, Xuesong B, Perry NP. Selected physical and mechanical properties of giant timber bamboo grown in South Carolina. Forest Prod. J. 1994;44(9):40-46.
11. Chaowana P. Bamboo: An Alternative Raw Material for Wood and Wood-Based Composites. Journal of Materials Science Research. 2013;2(2).
12. Anwar UMK, Zaidon A, Hamdan H, Tamizi MM. Physical and Mechanical properties of *Gigantochloa scorthchinii* Bamboo Splits and Strips. Journal of Tropical Forest Science. 2005; 17(1): 1-12.
13. Liese W. The anatomy of bamboo culms. International Network for Bamboo and Rattan, Beijing, People's Republic of China. 1998; 18.
14. Qi J, Xie J, Hse C, Shupe TF. Analysis of *Phyllostachys pubescens* Bamboo Residues for Liquefaction: Chemical Components, Infrared Spectroscopy, and Thermogravimetry. Bio Resources. 2013;8(4):5644-5654.
15. Zheng Y, Pan Z, Zhang R, Jenkins BM, Blunk S. Properties of medium-density particleboard from saline Athel wood. Elsevier. 2005;23:318–326.
16. Biswas D, Bose SK, Hossain MM. Physical and mechanical properties of urea formaldehyde-bonds particleboard made from bamboo waste. International Journal of Adhesion and Adhesives. 2011;31:84-87.
17. ANSI (American National Standards Institute). American national standard for particleboard. ANSI/A208.1," Gaithersburg, Maryland: Composite Panel Association; 2009.
18. Kasim J, Jalil A, Ahmad H, Harun J, Abd ZA, Mohmod L, Yusof M. Properties of particleboard manufactured from commonly utilized Malaysian bamboo (*Gigantochloa scorthchinii*), Non-wood Division, Forest Research Institute Malaysia, 52109 Kepong, Kuala Lumpur, Malaysia, ISSN: 1511-3701. 2001;151–157.
19. Vital BR, Lehmann WF, Boone RS. How species and board densities affect properties of exotic hardwood particleboards. For. Prod. J. 1974;24(12):37-45.
20. Kelly MW. Critical literature review of relationships between processing parameters and physical properties of particleboard. General Technical Report FPL-10. Forest Products Laboratory Forest Service U.S. Department of Agriculture. 1977;40-62.
21. Tomalang FN, Lopez AR, Semara JA, Casin RF, Espiloy ZB. Properties and utilization of Philippine erect bamboo. In International Seminar on Bamboo Research in Asia held in Singapore, May 28-30. International Development Research Center and the International

- Union of Forestry Research Organization. 1980;266-275.
22. Wu Q. Comparative properties of bagasse particleboard. International Symposium on Utilization of Agricultural and Forest Residue. Nanjing, China. 2001;1:8.
23. Ashaduzzaman M, Sharmin A. Utilization of fast growing species for manufacturing medium density particleboard in Bangladesh. Proceedings of the International Panel Products Symposium. Cardiff, UK. 2007;333-400.

© 2015 Alam et al.; This is an Open Access article distributed under the terms of the Creative Commons Attribution License (<http://creativecommons.org/licenses/by/4.0>), which permits unrestricted use, distribution, and reproduction in any medium, provided the original work is properly cited.

Peer-review history:

The peer review history for this paper can be accessed here:
<http://www.sciencedomain.org/review-history.php?iid=969&id=31&aid=8347>